



Introduction of INR18650-25R



SAMSUNG SDI

Oct. 2013



Energy Business Division

This material is proprietary to Samsung SDI Co., Ltd. It shall not be used, reproduced, copied, disclosed, transmitted, in whole or in part, without the express written consent of Samsung SDI Co., Ltd.



SAMSUNG SDI



INR18650-25R

- **Specification**
- **Capacity (0.2C vs. 10A)**
- **AC/DC impedance**
- **Capacity & temperature vs. discharge capacity**
- **Energy & avg. voltage at different current**
- **Cycle life**
- **Pulse cycle life**
- **Low temperature voltage profile at 10A**
- **Storage characteristics**
- **Safety test**



Type		Spec.	Typical INR18650-25R
Chemistry		NCA	NCA
Dimension (mm)	Diameter	18.33 ± 0.07	18.33 ± 0.07
	Height	64.85 ± 0.15	64.85 ± 0.15
Weight (g)		Max. 45.0	43.8
Initial IR (mΩ AC 1kHz)		≤ 18	13.20 ± 2
Initial IR (mΩ DC (10A-1A))		≤ 30	22.15 ± 2
Nominal Voltage (V)		3.6	3.64
Charge Method (100mA cut-off)		CC-CV (4.2±0.05V)	CC-CV (4.2±0.05V)
Charge Time	Standard (min), 0.5C	180min	134min
	Rapid (min), 4A	60min	55min
Charge Current	Standard current (A)	1.25	1.25
	Max. current (A)	4.0	4.0
Discharge	End voltage (V)	2.5	2.5
	Max. cont. current (A)	20	20
	Max. momentary pulse (A, <1sec)	100	100
Rated discharge Capacity	Standard (mAh) (0.2C)	2,500	2,560
	rated (mAh) (10A)	2,450	2,539

Capacity _ 0.2C vs. 10A



PROPRIETARY AND
CONFIDENTIAL


▪ 0.2C capacity

Cell	Capacity(Ah)	Energy(Wh)	Avg. volt(V)
1	2.555	9.36	3.66
2	2.557	9.37	3.66
3	2.557	9.37	3.67
4	2.564	9.39	3.66
5	2.565	9.40	3.66
Avg.	2.560	9.38	3.66

▪ 10A capacity

Cell	Capacity(Ah)	Energy(Wh)	Avg. volt(V)
1	2.533	8.71	3.44
2	2.531	8.70	3.43
3	2.539	8.74	3.44
4	2.544	8.77	3.45
5	2.548	8.76	3.44
Avg.	2.539	8.74	3.44


■ AC-IR

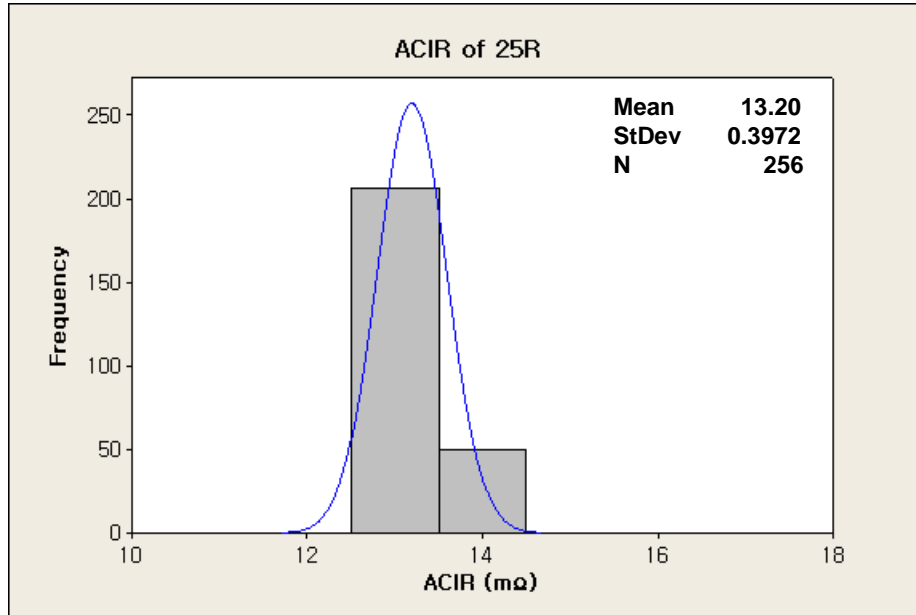

AC-IR

13.20 ± 2mΩ

■ DC-IR

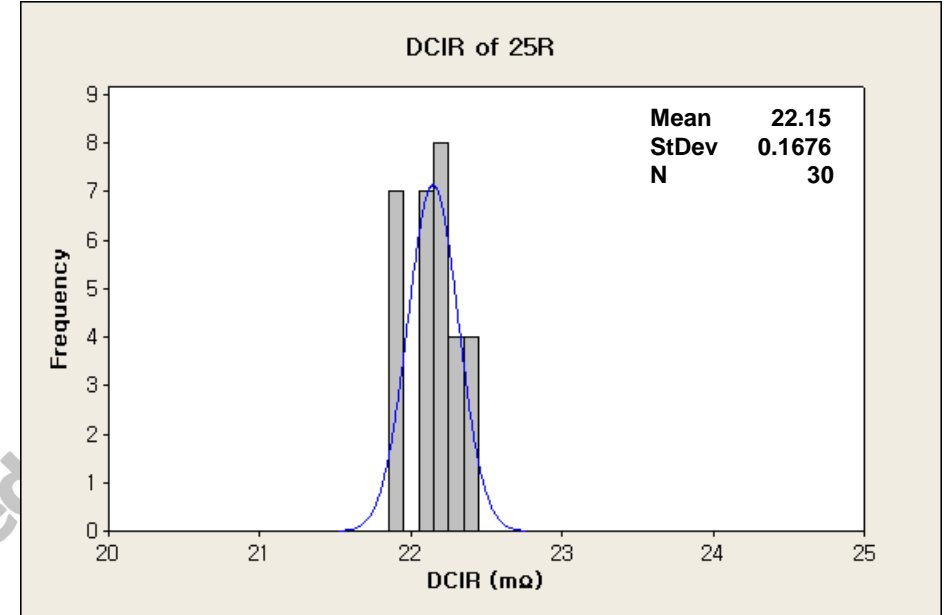


DC-IR

22.15 ± 2mΩ

Capacity & Temperature vs. discharge capacity

PROPRIETARY AND
CONFIDENTIAL

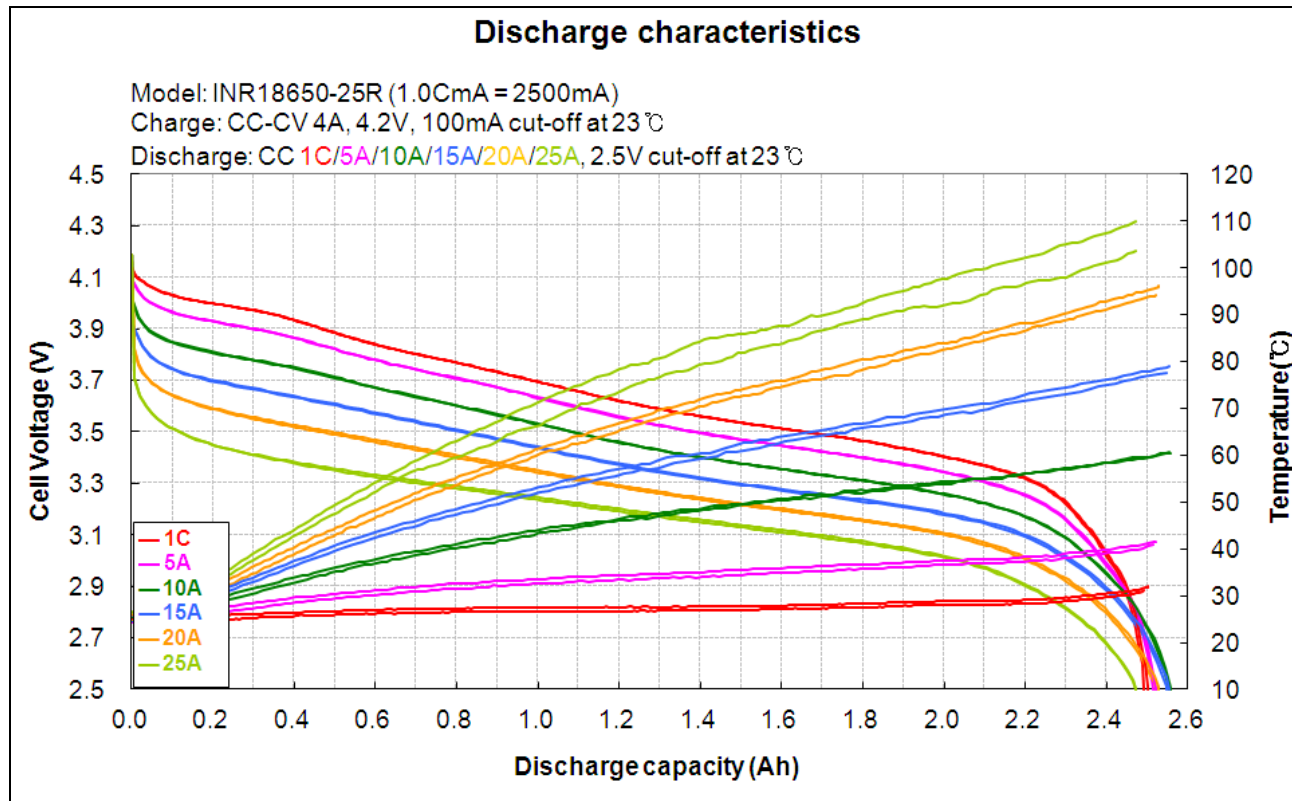


IEEE/UL Battery
 Sizing by
MooreU
 610-952-6067
 www.mooreu.com

Discharge current						
	1C	5A	10A	15A	20A	25A
Capa.(Ah)	2.496	2.518	2.556	2.550	2.525	2.472
Temp.(°C)	31.6	41.2	60.6	78.4	95.2	106.8
Time(min.)	59.9	30.2	15.3	10.2	7.6	5.9

Energy & Avg. voltage at different current

PROPRIETARY AND
CONFIDENTIAL

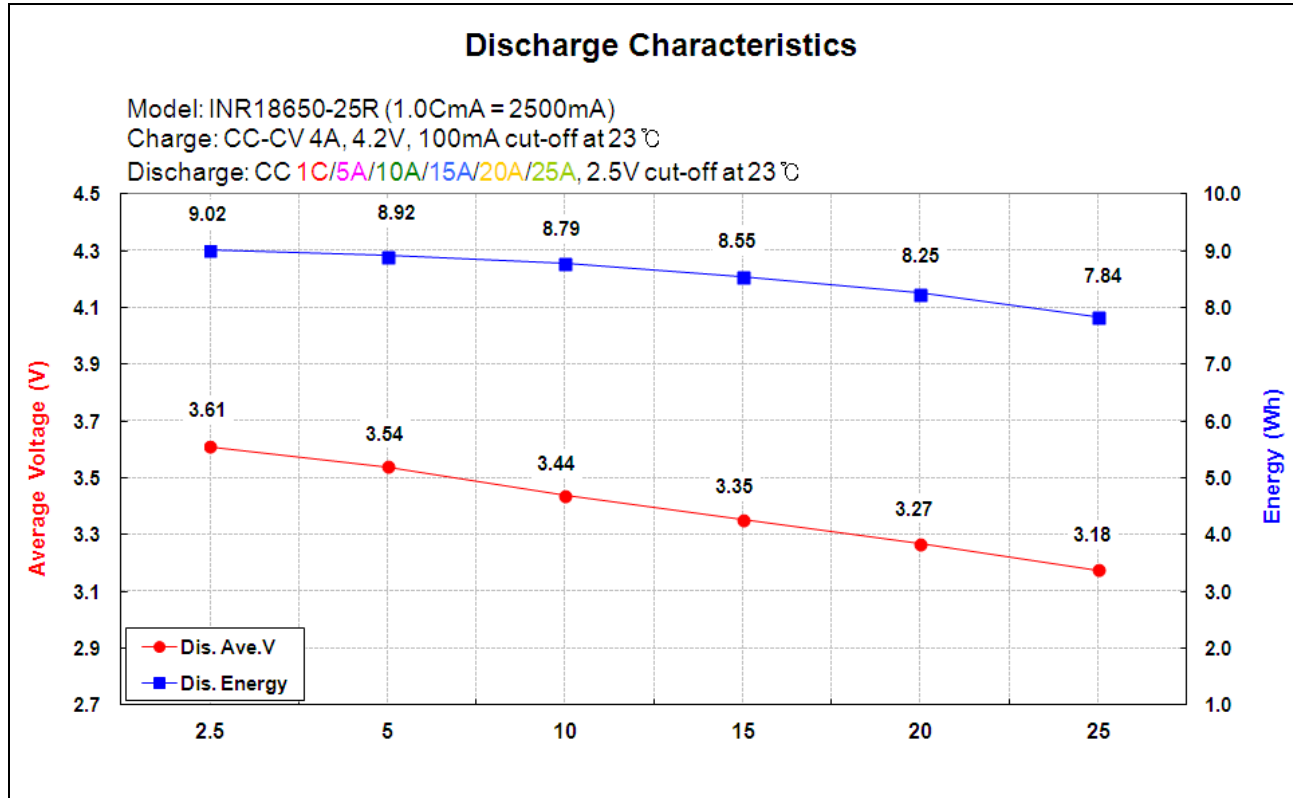

Discharge current						
	1C	5A	10A	15A	20A	25A
Energy(Wh)	9.02	8.95	8.79	8.55	8.25	7.84
Avg. voltage(V)	3.61	3.54	3.44	3.35	3.27	3.18

Cycle life _ 20A cycle

PROPRIETARY AND
CONFIDENTIAL

IEEE/UL Battery
Sizing by
MooreU
610-952-6067
www.mooreu.com




20A discharge cycle life of 25R

Ambient temperature : 23°C

Test method : Charge 4A 4.2V 100mA cutoff, rest 10min.

Discharge 20A 2.5V cutoff, rest 30min.

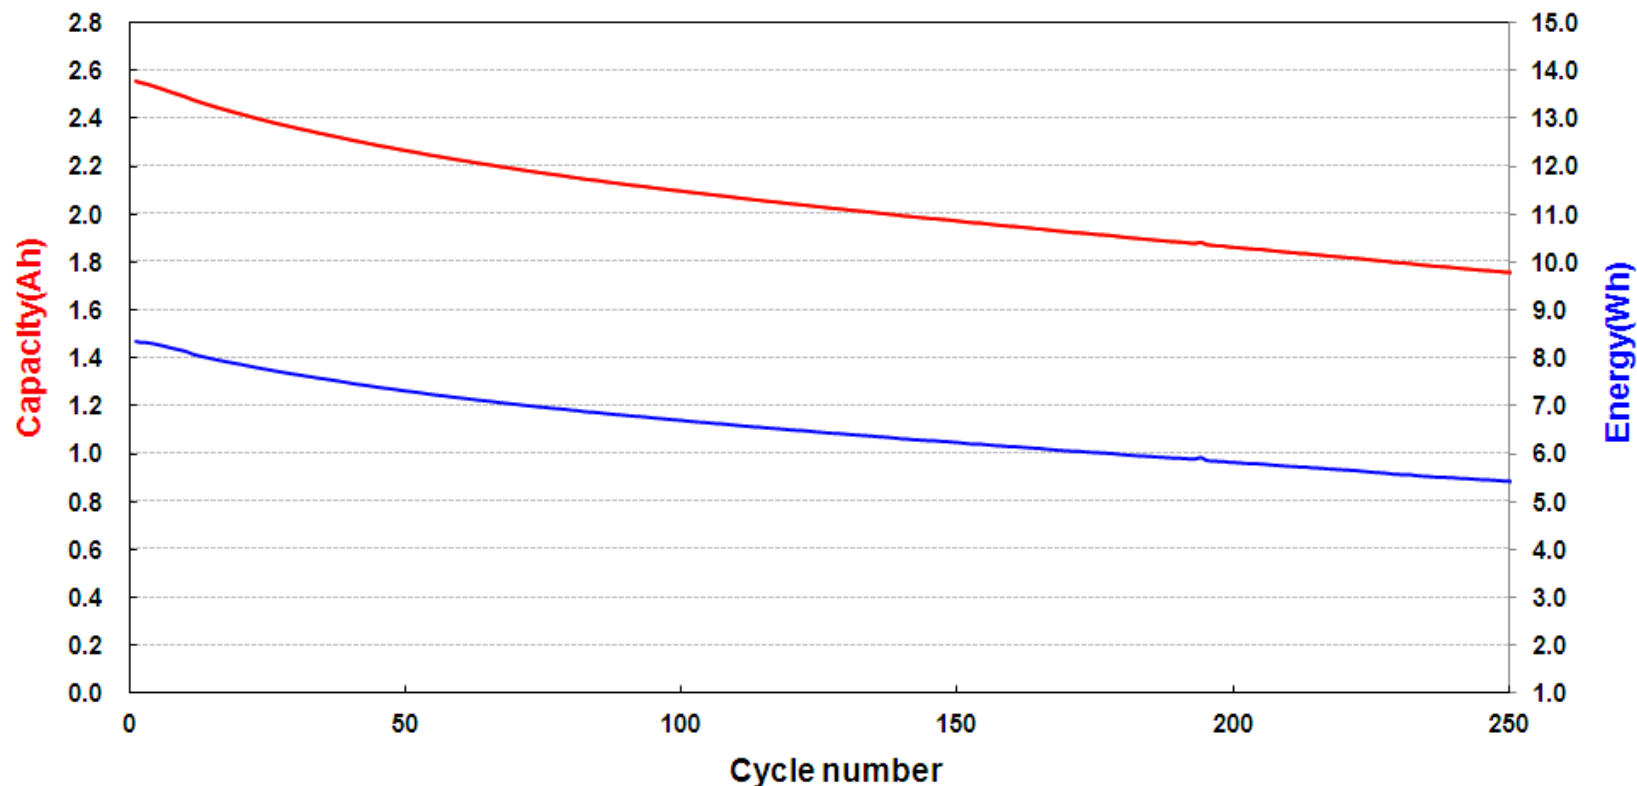

Cycle life _ 30A cycle(70°C T-cut)

PROPRIETARY AND
CONFIDENTIAL




30A discharge cycle life of 25R

Ambient temperature : 23°C

Test method : Charge 4A 4.2V 100mA cutoff, rest 10min.

Discharge 30A 2.5V cutoff, rest 30min. (after T-cut 70°C, re-discharge below 50°C)

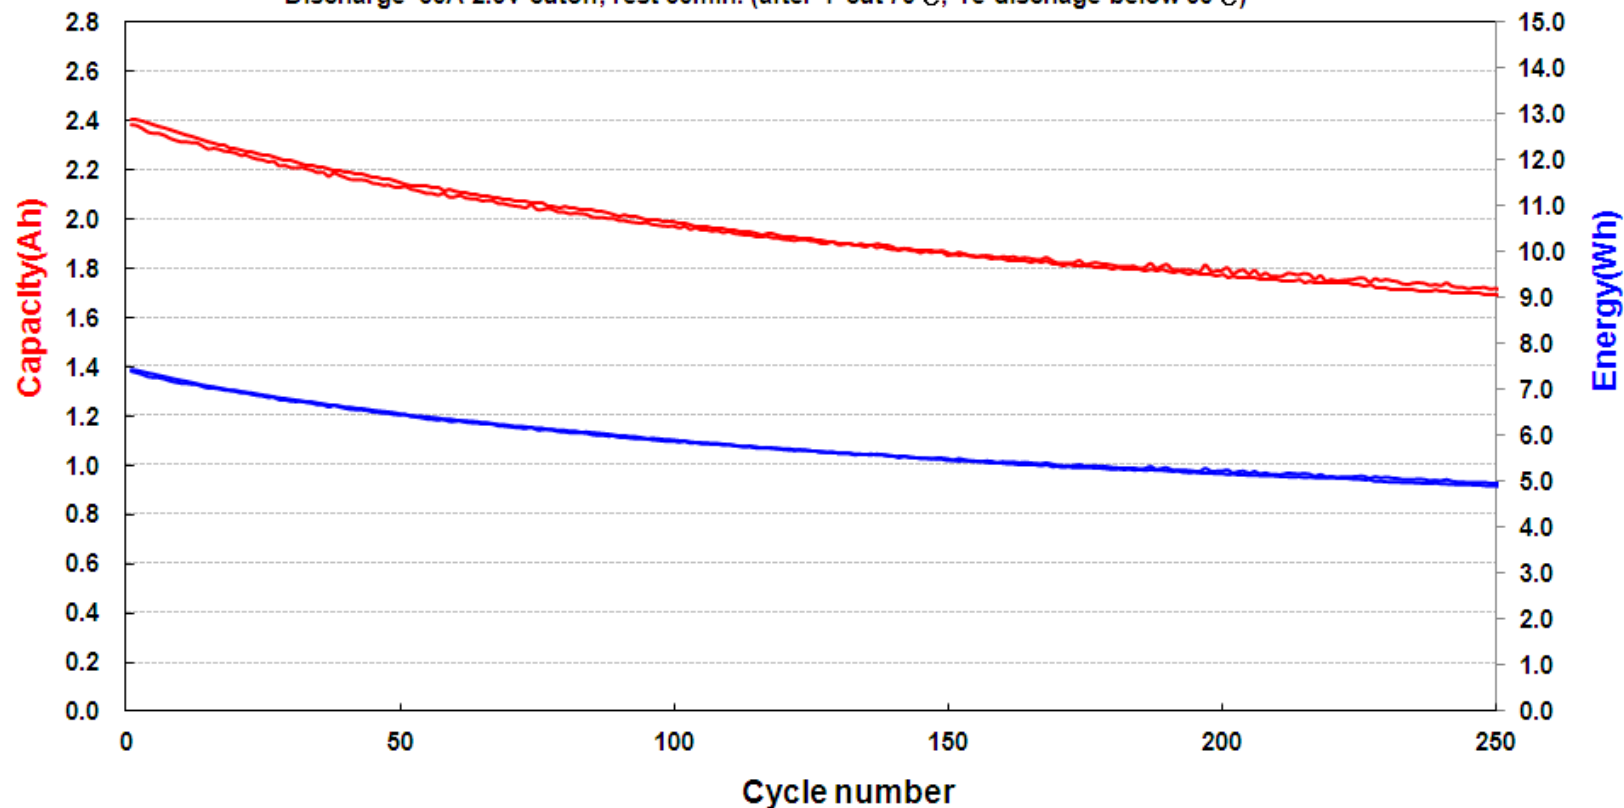

High pulse cycle life

PROPRIETARY AND
CONFIDENTIAL

IEEE/UL Battery
Sizing by
MooreU
610-952-6067
www.mooreu.com




High pulse discharge cycle life of 25R

Ambient temperature : 23°C

Test Method : Charge 4A 4.2V 100mA cutoff, rest 10min.

Discharge 65A·1sec - 40A·5sec - 30A·6sec, 1.5V cutoff, rest 30min.

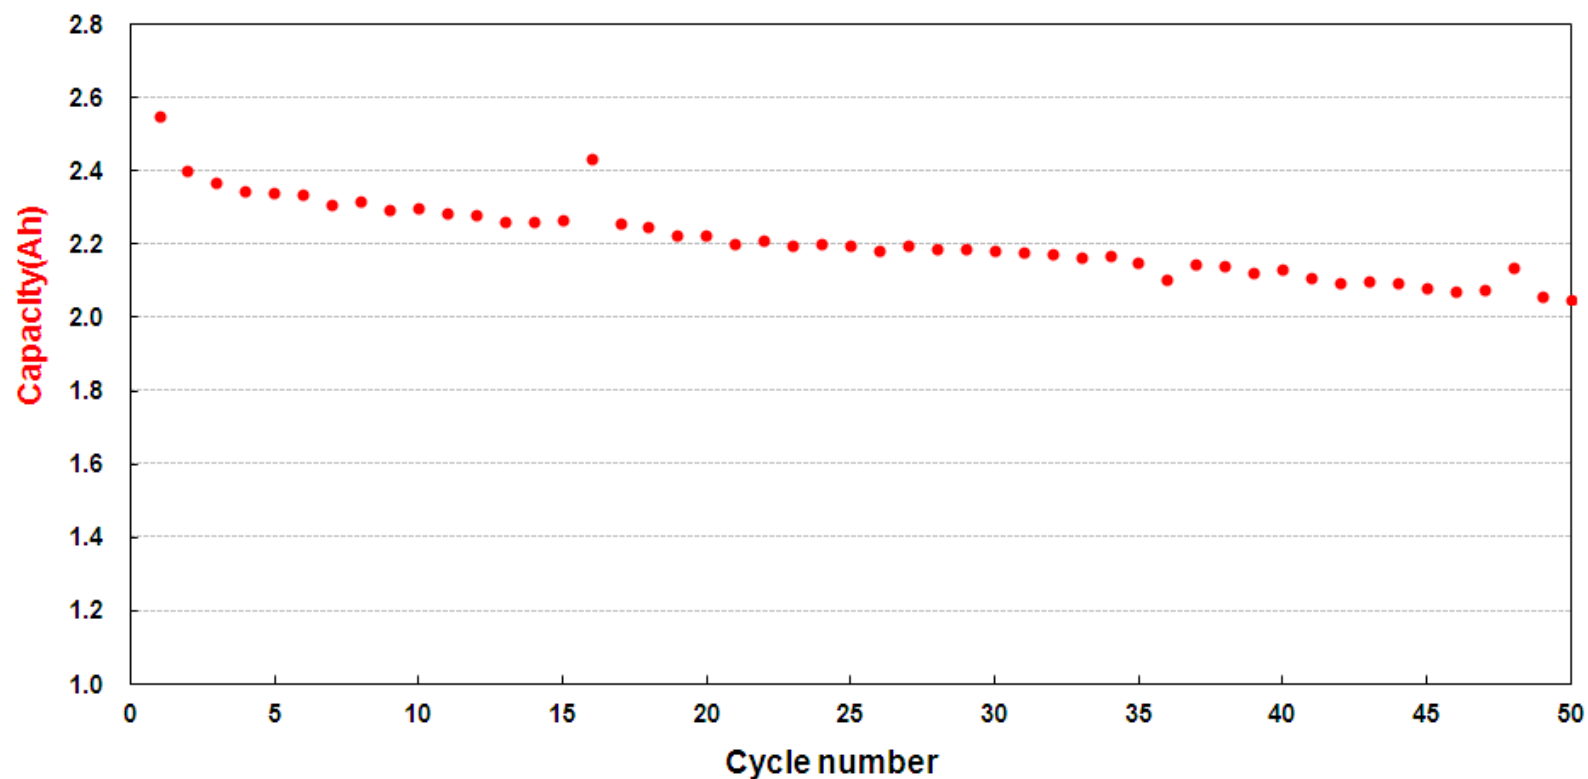

High pulse cycle life 2

PROPRIETARY AND
CONFIDENTIAL

IEEE/UL Battery
Sizing by
MooreU
610-952-6067
www.mooreu.com




High pulse discharge cycle life 2 of 25R

Ambient temperature : 23°C


Test Method : Charge 4A 4.2V 100mA cutoff, rest 10min.

Discharge 95A-0.5sec - 80A-0.5sec - 45A-5sec - 30A-6sec - rest 12sec, 1.5V cutoff, rest 30min.

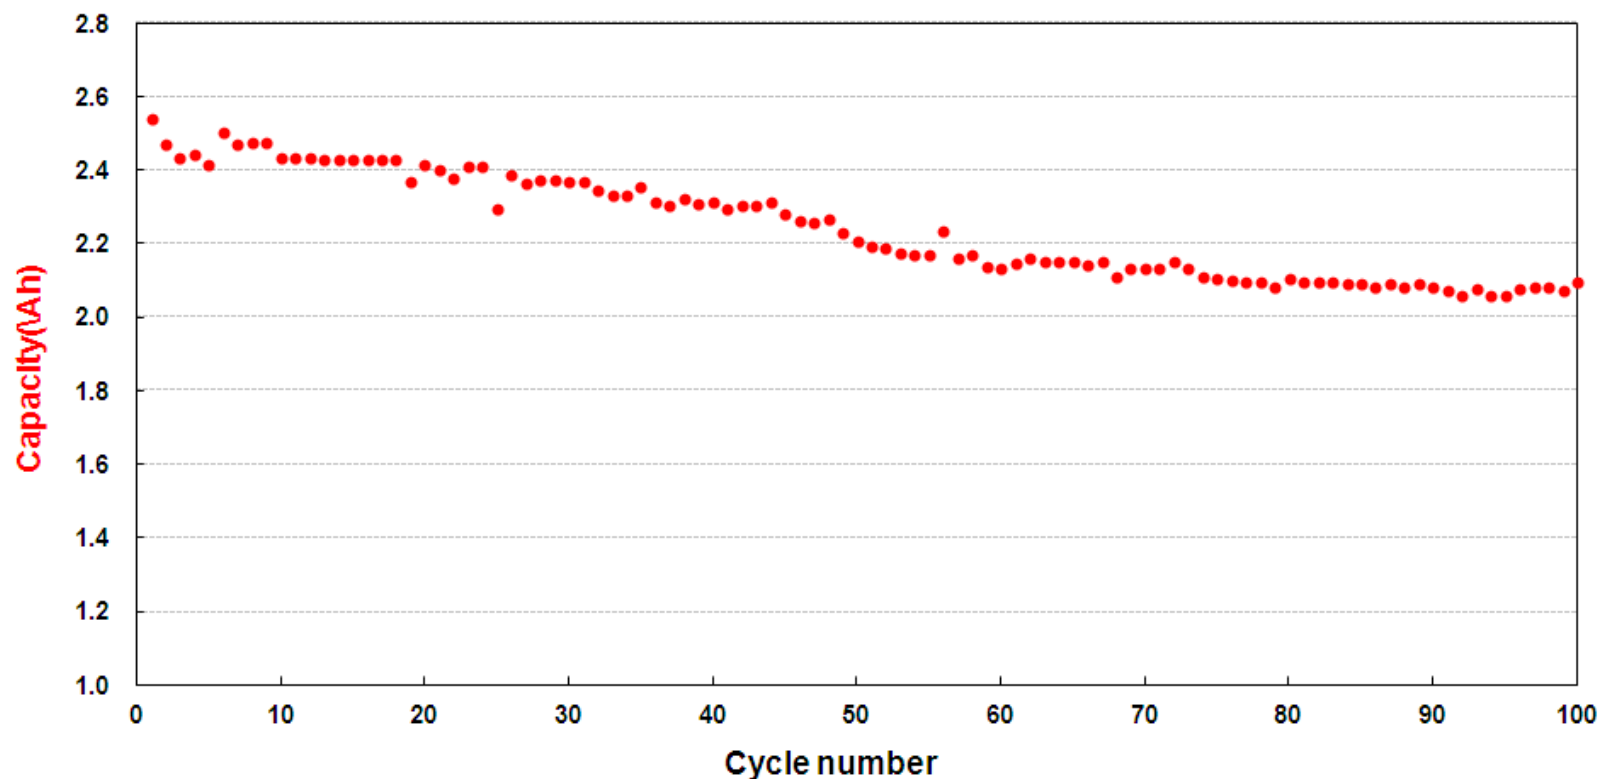

Low temperature discharge (10A)

**PROPRIETARY AND
CONFIDENTIAL**

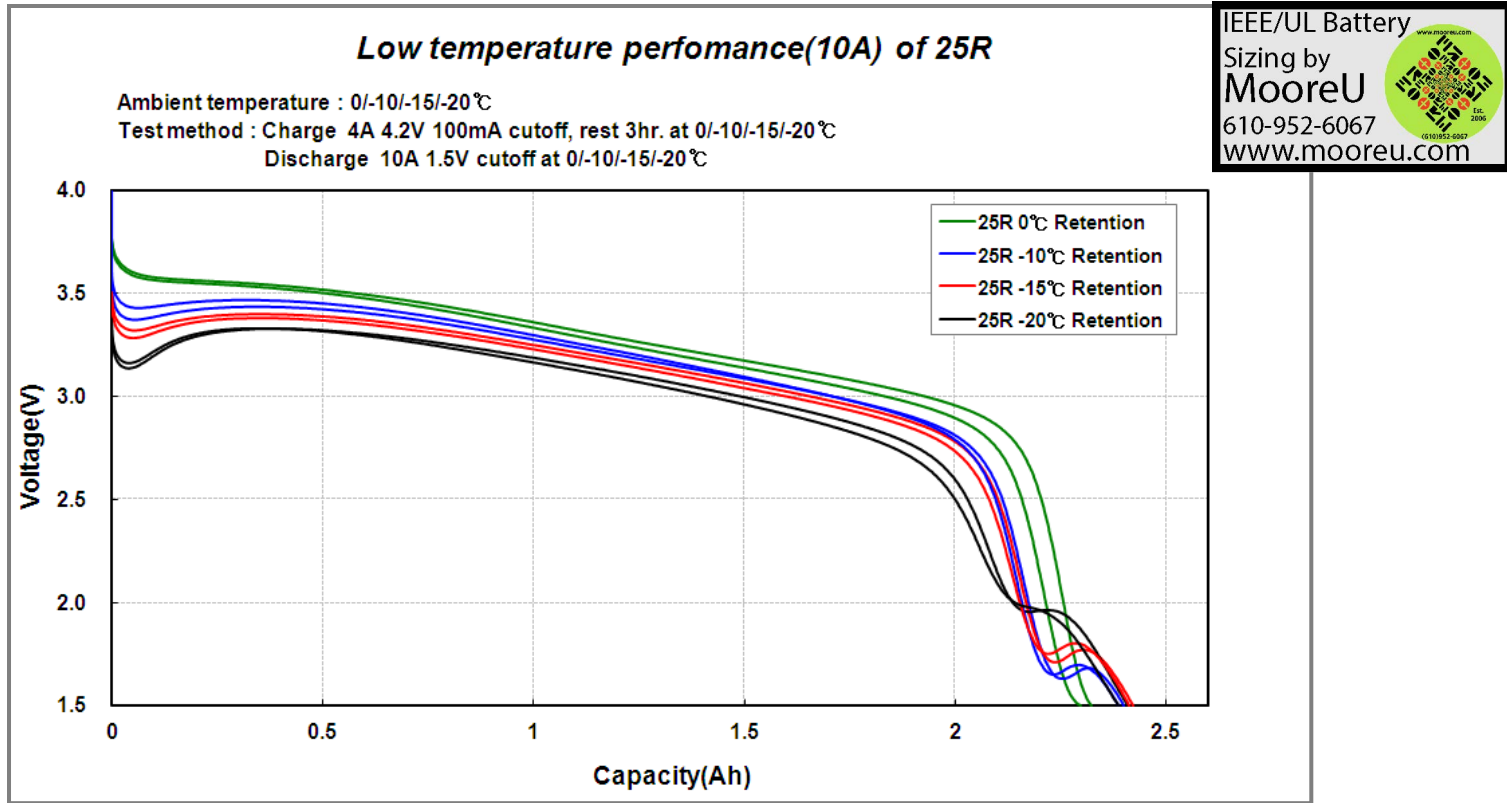


IEEE/UL Battery
 Sizing by
MooreU
 610-952-6067
 www.mooreu.com




	0 °C		-10 °C		-15 °C		-20 °C	
	Capacity(Ah)	Capa.(%)	Capacity(Ah)	Capa.(%)	Capacity(Ah)	Capa.(%)	Capacity(Ah)	Capa.(%)
10A	2.323	92.9	2.398	95.9	2.413	96.5	2.407	96.3
	2.298	91.9	2.385	95.4	2.421	96.8	2.386	95.4
Avg.	2.310	92.4	2.392	95.7	2.417	96.7	2.397	95.9

Recovery

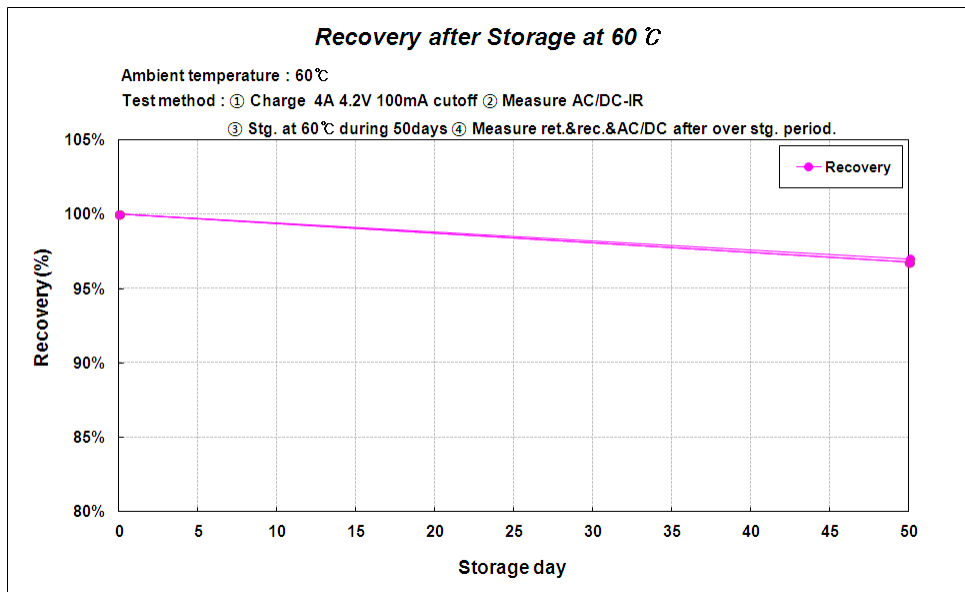


Retention

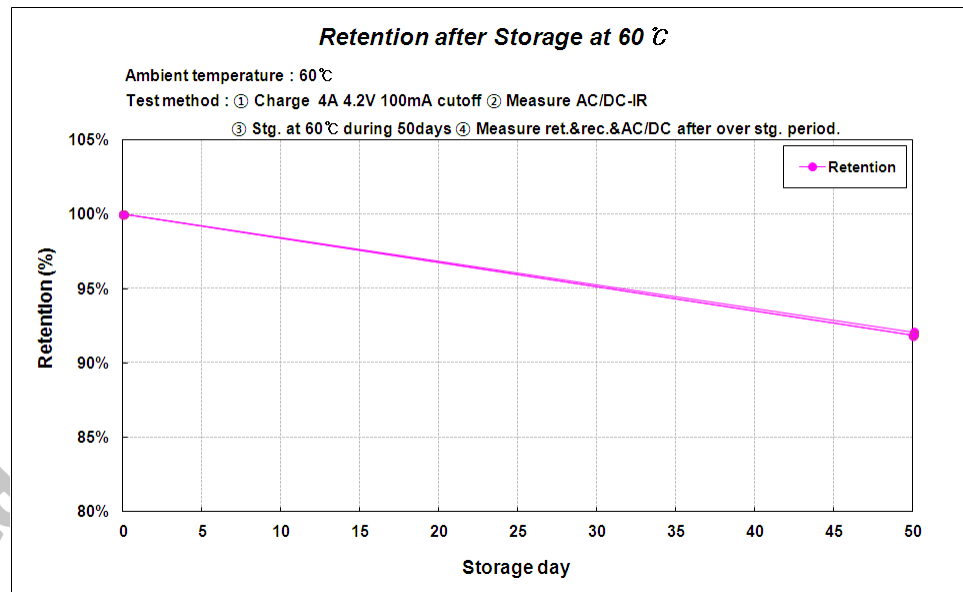


Storage at 60°C

storage day	initial			after storage				Ratio(%)			
	ACIR	DCIR	Capacity	ACIR	DCIR	Retention	Recovery	ACIR	DCIR	Retention	Recovery
50	13.2	20.2	2597	15.3	29.3	2122	2393	115.8	145.2	81.7	92.1

■ AC-IR

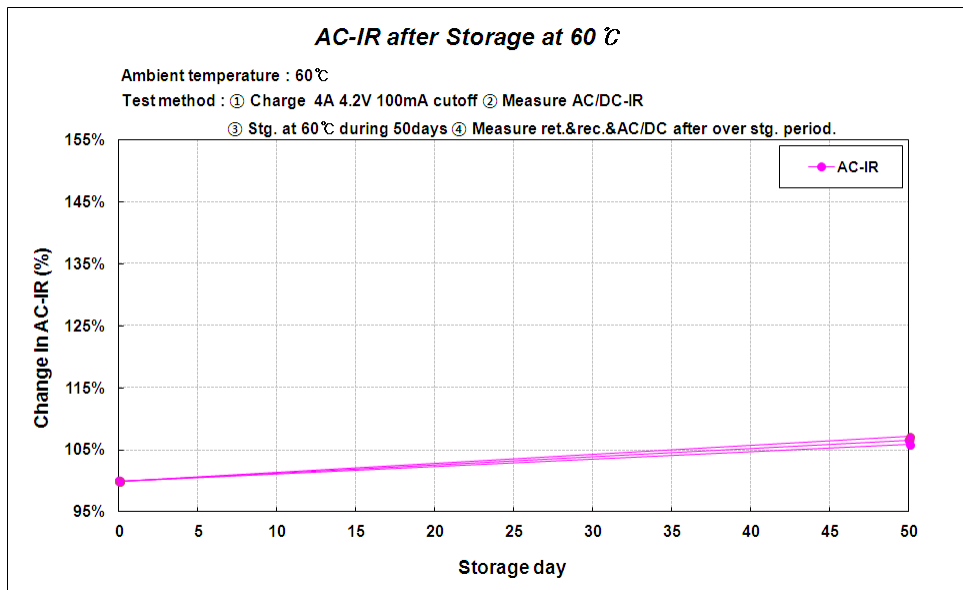

■ DC-IR

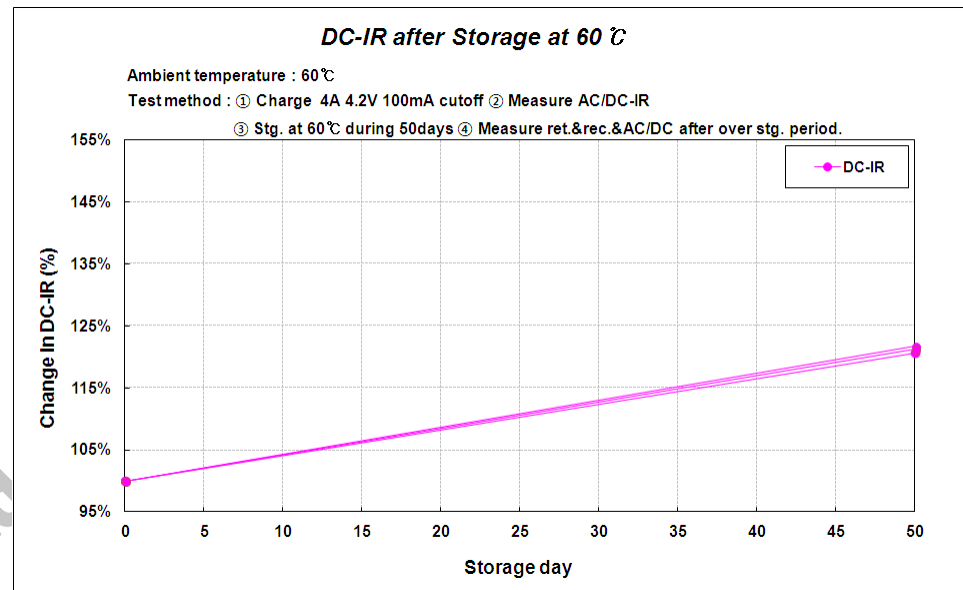

Storage at 60 °C

storage day	initial			after storage				Ratio(%)			
	ACIR	DCIR	Capacity	ACIR	DCIR	Retention	Recovery	ACIR	DCIR	Retention	Recovery
50	13.2	20.2	2597	15.3	29.3	2122	2393	115.8	145.2	81.7	92.1

Safety test



PROPRIETARY AND CONFIDENTIAL

Test item	Spec.	Results		OK/NG	Remark		
		Results	Max. temp.				
Electrical Abuse	Overcharge	20A 20V(UL)	L1	3L1	115.6	OK	
	Short circuit	10mΩ at 23°C	L1	3L1	55.0	OK	
Mechanical Abuse	Impact	UL	L1	5L0	22.6	OK	
	Crush	UL	L1	5L0	23.9	OK	
Thermal Abuse	Hot oven	140°C	L1	3L1	144.0	OK	

